

Figure 2: Summary of G2 Falcon UF Gravity Test Results

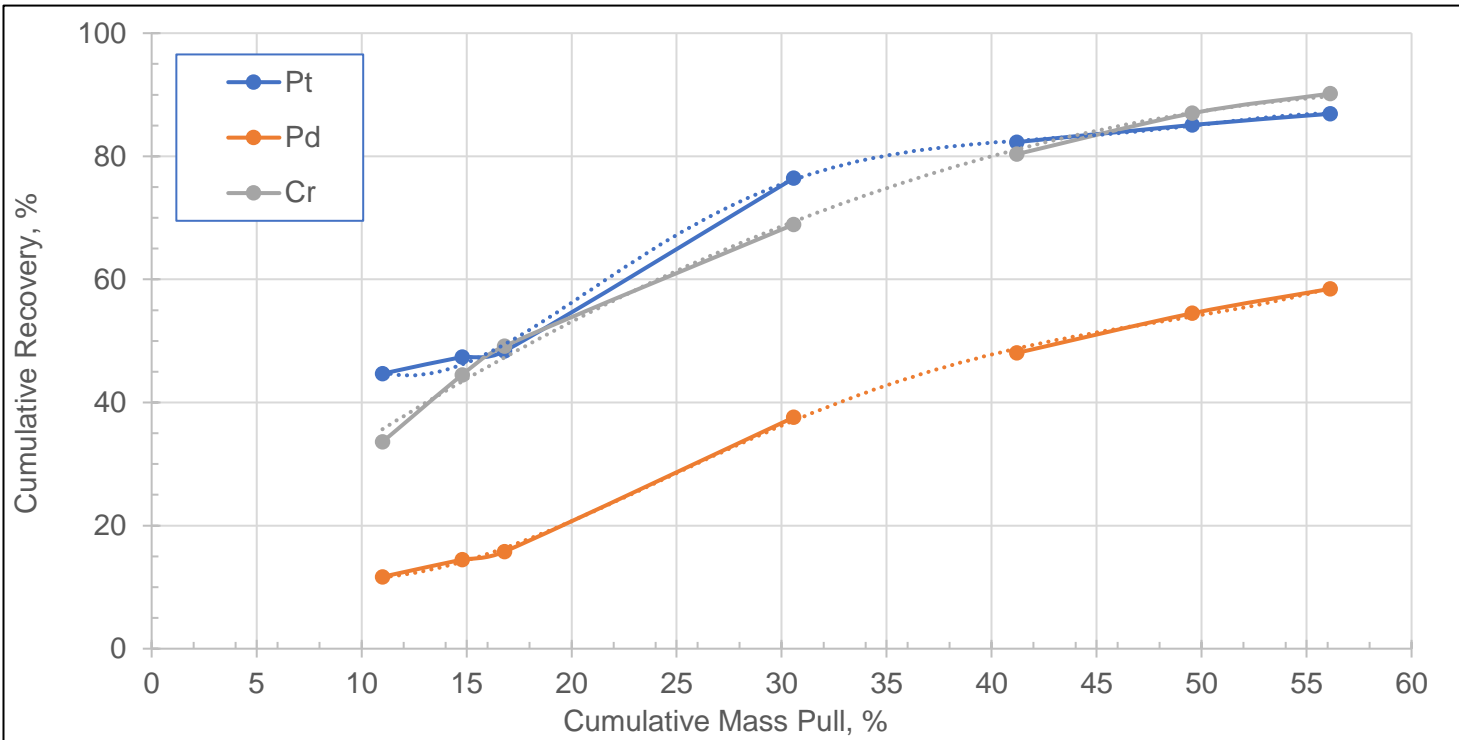


Table 4: Summary of G2 Falcon UF Gravity Test Results

Metallurgical Balance

Product		Mass		Assays, g/t				Distribution %			
		g	%	Pt, g/t	Pd, g/t	Cr, %	CO ₃ , %	Pt	Pd	Cr	CO ₃
Stage 1, Wilfley											
1	Pass 1 Concentrate	434	11.0	12.8	6.78	24.3	0.13	44.7	11.7	33.6	5.1
2	Pass 2 Concentrate	150	3.8	2.25	4.70	22.8	0.12	2.7	2.8	10.9	1.6
3	Pass 2 Middling 1	79.5	2.0	1.49	4.12	18.5	0.19	1.0	1.3	4.7	1.4
Stage 2, Falcon *											
4	Pass 1 Concentrate	544	13.8	6.42	10.1	11.4	0.29	28.1	21.8	19.7	14.3
5	Pass 2 Concentrate	420	10.6	1.74	6.28	8.55	0.30	5.9	10.5	11.4	11.4
6	Pass 3 Concentrate	330	8.4	1.05	4.92	6.33	0.32	2.8	6.4	6.7	9.6
7	Pass 4 Concentrate	260	6.6	0.87	3.86	3.86	0.34	1.8	4.0	3.2	8.0
	Pass 4 Tailing	1,733	43.9	0.94	6.04	1.78	0.31	13.1	41.5	9.8	48.6
	Head (Calc.)	3,951	100.0	3.15	6.38	7.95	0.28	100.0	100.0	100.0	100.0
	Head (Direct.)	4,000		3.83	6.86	7.66					

* Note that the masses shown in the table are based on the assumption that the entire mass of product NOT included in the Stage 1 products shown above

Combined Products

Stage 1, Wilfley											
	Product 1	434	11.0	12.8	6.78	24.3	0.13	44.7	11.7	33.6	5.1
	Product 1+2	585	14.8	10.1	6.25	23.9	0.13	47.4	14.5	44.5	6.7
	Product 1-3	664	16.8	9.06	5.99	23.3	0.13	48.4	15.8	49.2	8.1
Wilfley+ Falcon											
	Product 1-4	1,208	30.6	7.87	7.84	17.9	0.20	76.4	37.6	68.9	22.4
	Product 1-5	1,628	41.2	6.29	7.44	15.5	0.23	82.3	48.0	80.3	33.8
	Product 1-6	1,958	49.6	5.41	7.01	14.0	0.24	85.1	54.5	87.0	43.4
	Product 1-7	2,218	56.1	4.87	6.64	12.8	0.26	86.9	58.5	90.2	51.4